

HexPly® M10/38%/UD300/CHS

Epoxy Matrix

Product Data Sheet

Description

HexPly® M10/38%/UD300/CHS is a UD High Strength Carbon Epoxy prepreg, whereby M10 is the resin type; 38% is the resin content by weight; UD300 is the reinforcement reference and CHS represents High Strength Carbon fibre. **This data sheet is complementary to the M10 resin data sheet, which should be consulted for additional information.**

Reinforcement Data

Nominal Areal Weight	g/m ²	300	0°	90°
Composition		UD	300	-
Fibre Type		High Strength Carbon		
Nominal Fibre Density	g/cm ³	1.8		

Matrix Properties

Glass transition temperature of laminate (Cure cycle: 60 min @ 120°C)	°C	130 (DMA onset, 5°C/min, 1Hz, 30µm)
Nominal Resin Density	g/cm ³	1.2

Prepreg Data



Nominal Areal Weight	g/m ²	484
Nominal Resin Content	weight%	38
Volatiles	weight %	Hot Melt
Tack level		Medium

Processing

Cure Cycle		@ 85 °C	960 min
	or	@ 120 °C	60 min
	or	@ 150 °C	10 min
Recommended heat up rate		°C/min	3 - 5°C/min
Pressure (gauge)		bar	0.3 to 5

The optimum cure cycle, heat up rate and dwell period depend on part size, laminate construction, oven capacity and thermal mass of tool.

Cured Laminate Properties (nominal composite density 1.51 g/cm³)

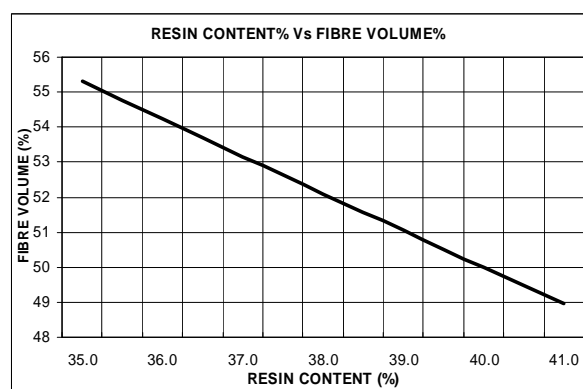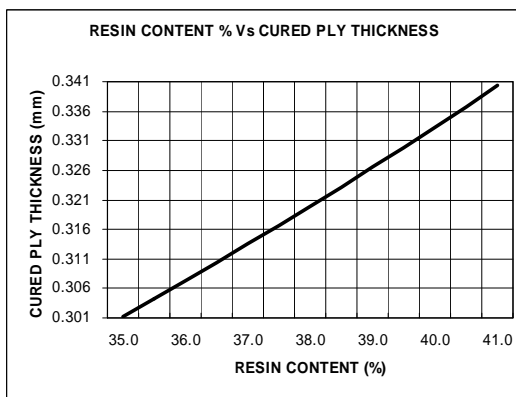

The above graphs enable the fibre volume content of a laminate to be estimated using the measured cured ply thickness. The calculation assumes no resin loss.





HexPly® M10/38%/UD300/CHS

Mechanical Properties (at 60% fibre volume)

Mechanical Properties are based on 120°C cure for 60 mins at 3 bar pressure and 0.8 bar vacuum.

Data is the result from several tests on autoclave-cured laminates. Some of the values achieved will have been higher, and some lower, than the figure quoted. These are nominal values.

0° (Dry & RT)	Tensile	Flexural	ILSS	Compression
Strength (MPa)	1700	1400	80	1250
Modulus (GPa)	130	127	-	110
Test Method	EN 2561 B	EN 2562	EN 2563	EN 2850 B

Prepreg Storage Life

- **Shelf Life¹**: 12 months at -18°C/0°F (from date of manufacture)
- **Out Life²**: 60 days at Room Temperature
- **Tack Life³**: 60 days at Room Temperature

¹Shelf Life: the maximum storage life for HexPly® prepreg, upon receipt by the customer, when stored continuously, in a sealed moisture-proof bag, at -18°C/0°F or 5°C/41°F. To accurately establish the exact expiry date, consult the box label.

²Out Life: the maximum accumulated time allowed at room temperature between removal from the freezer and cure.

³Tack Life: the time, at room temperature, during which prepreg retains enough tack for easy component lay-up.

Prepreg should be stored as received in a cool dry place or in a refrigerator. After removal from refrigerator storage, prepreg should be allowed to reach room temperature before opening the polyethylene bag, thus preventing condensation. (A full reel in its packing can take up to 48 hours).



HexPly® M10/38%/UD300/CHS

Precautions for Use

The usual precautions when handling uncured synthetic resins and fine fibrous materials should be observed, and a Safety Data Sheet is available for this product. The use of clean disposable inert gloves provides protection for the operator and avoids contamination of material and components.

Important

All information is believed to be accurate but is given without acceptance of liability. All users should make their own assessment of the suitability of any product for the purposes required. All sales are made subject to our standard terms of sale which include limitations on liability and other terms.

® Copyright Hexcel Corporation
HexPly® M10/38%/UD300/CHS – July/2005 a

For further information, please contact your nearest Hexcel sales office, or visit www.hexcel.com

Australia

Suite 2, 86 Grimshaw Street
Greensborough, Victoria 3088
Tel: **61** 3 9432 7100
Fax: **61** 3 9432 7200

China

Room B707, Yin Hai Bldg.
250 Cao Xi Rd
Shanghai 200233
Tel: **86** 21 6483 6741/2
Fax: **86** 21 6483 6744

Japan - Joint Venture

DIC - Hexcel Limited
7F Nissei Bldg., 6-2-8
Sotokanda,
Chiyoda-ku, Tokyo 101-0021
Tel: **81** (0)3 5812 3361
Fax: **81** (0)3 3837 7522

USA

900 Main Street South,
Building 1, Suite 104,
Southbury, CT 06488
Tel: **1** 203 267 1414
Fax: **1** 203 267 1561

Austria

Industriestrasse 1
A-4061, Pasching
Tel: **43** (0)7229 7720
Fax: **43** (0)7229 772299

France

ZI La Plaine, B.P.27 Dagneux
01121 Montluel CEDEX
Tel: **33** (0)4 72 25 26 27
Fax: **33** (0)4 72 25 27 30

Spain

Bruselas, 10 - 16
Polig. Ind. "Ciudad de Parla"
28980 Parla, Madrid
Tel: **34** 91 664 4900
Fax: **34** 91 698 4914

USA

2350 Airport Freeway, Suite
550,
Bedford, TX 76022-6027
Tel: **1** 817 315 3939
Fax: **1** 817 571 8629

Belgium

Rue Trois Bourdons, 54
B-4840 Welkenraedt
Tel: **32** 87 307 411
Fax: **32** 87 882 895

Germany

Ottenbecker Damm 1
21684 Stade
Tel: **49** 4141 7879-00
Fax: **49** 4141 7879-01

United Kingdom

Duxford, Cambridge
CB2 4QD
Tel: **44** (0)1223 833141
Fax: **44** (0)1223 838808

USA

16310 NE 80th Street, Suite
102
Redmond, WA 98052
Tel: **1** 425 558 440
Fax: **1** 425 861 5847

Brazil

Av.J.Guilhermino, 474/72
S.J.Campos, SP 12210-130
Tel: **55** 12 3941 2242
Fax: **55** 12 3923 1186

Italy

Via San Cristoforo, 44
21047 Saronno (VA)
Tel: **39** 02 96709082
Fax: **39** 02 9600809

USA

11711 Dublin Blvd.
Dublin, CA 94568-2832
Tel: **1** 925 551 4900
Fax: **1** 925 828 9202